

Vibrational anisotropy and quadrupole interactions of Fe substituted into Mn site of the charge and orbitally ordered and disordered layered manganites $\text{LnBaMn}_{1.96}\text{Fe}_{0.04}\text{O}_5$ and $\text{LnBaMn}_{1.96}\text{Fe}_{0.04}\text{O}_6$ (Ln=Y, Gd, Sm, La, etc.)

A. I. Rykov,^{1,2} Y. Ueda³, K. Nomura¹, and M. Seto⁴

¹The University of Tokyo, Hongo 7-3-1, 113-8656, Japan,
²Technology Crystals Laboratory "Tecrys", Institutskaya 4/1,
 630090, Novosibirsk, Russia, ³Institute for Solid State Physics,
 University of Tokyo, 5-1-5, Kashiwanoha, Chiba 277-8581,
 Japan, ⁴Research Reactor Institute, Kyoto University,
 Noda, Kumatori-machi, Osaka 590-0494, Japan*
 (Dated: March 23, 2009)

A-site ordered manganites $\text{LnBaMn}_{1.96}\text{Fe}_{0.04}\text{O}_5$ and $\text{LnBaMn}_{1.96}\text{Fe}_{0.04}\text{O}_6$ are investigated by x-ray full-profile diffraction and Mössbauer spectroscopy. Powder samples were oriented with preferred orientation of platy crystallites in the plane of sample surface. March-Dollase function of preferred orientation was employed in analysing both the Rietveld patterns and the Mössbauer spectra. Combined effects of preferred orientation and vibrational anisotropy on the line area asymmetry of Mössbauer doublet are analysed. Constructive and destructive interference between the effects of texture and vibrational anisotropy is observed in $\text{LnBaMn}_{1.96}\text{Fe}_{0.04}\text{O}_6$ and $\text{LnBaMn}_{1.96}\text{Fe}_{0.04}\text{O}_5$, respectively. Both series of the manganites show the main axis of electric field gradient perpendicular to layers ($V_{zz} \parallel c$) with $V_{zz} > 0$ in oxygen-poor series and $V_{zz} < 0$ in oxygen-rich series. Charge-orbital order (COO) melting around Fe dopants explains the single-site spectra observed for several Ln in both "O₅" and "O₆" series, except $\text{LaBaMn}_{1.96}\text{Fe}_{0.04}\text{O}_5$. However, the short-range COO persists to be observed in magnetization and in x-ray patterns.

PACS numbers:

I. INTRODUCTION

The manganites $\text{LnBaMn}_2\text{O}_y$ present a novel class of layered materials, in which the layered arrangements of Y and Ba cations results into the regular architectures of the half-occupied e_g -orbitals of Mn^{3+} with the out-of-plane and in-plane orientations for $y = 5$ and $y = 6$, respectively. Both series enclose manganese in state of half-doping mixed valence. The orbital order is coupled to charge order, consisting in the alternations $\text{Mn}^{3+}/\text{Mn}^{2+}$ and $\text{Mn}^{3+}/\text{Mn}^{4+}$ for $y = 5$ and $y = 6$, respectively, along three axes, which are Cartesian for the majority of Ln's, but slightly oblique in monoclinic¹ or triclinic² YBaMn_2O_6 .

Owing to the layered structure the polycrystalline materials are highly susceptible to preferred orientation withstanding a simple quantitative description, except the special case of YBaMn_2O_6 . Recently, such a quantitative description was suggested³ to be useful in vibrational spectroscopy on powders of anisotropic materials. As a matter of fact, the oriented polycrystals consisting of platy crystallites can replace the single crystals in studies of a variety of anisotropic properties of materials, such as electric, magnetic or vibrational. Especially, when the polycrystalline material is a ferromagnet or a superconductor it can be subjected to a thorough texturing in an external magnetic field.

In this work, members of both the "O₅"⁴⁻⁶ and "O₆"^{1,2,7-10} families with Ln=Y, Gd, Sm, Nd, Pr, La and Ln= $\text{Sm}_{1-x}\text{Nd}_x$ solid solutions were doped with 2% of ⁵⁷Fe and investigated using Rietveld analysis, mag-

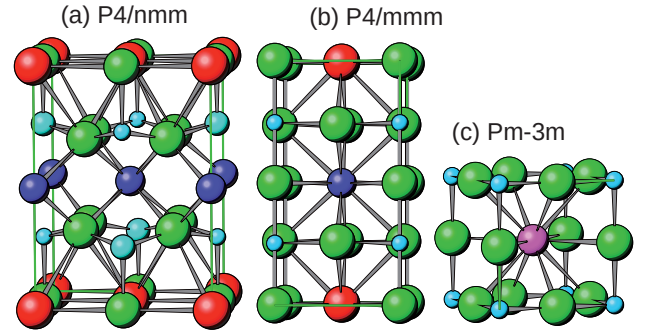


FIG. 1: The crystal structures and symmetry groups of the layer-ordered $\text{LnBaMn}_2\text{O}_5$ (a), $\text{LnBaMn}_2\text{O}_6$ (b) and disordered $\text{Ln}_{0.5}\text{Ba}_{0.5}\text{MnO}_3$ (c).

netization and Mössbauer spectroscopy on both random and oriented powders. We investigate the effect of the Fe substituents on the phase transitions known to occur in undoped systems. Clean samples exhibit the COO on the long-range scale observed previously via neutron diffraction^{1,2,7-9}. We show that the substitution smears some of the transitions and lowers the temperature for others.

In charge-ordered state, the Fe substituents display only one component Fe^{3+} in Mössbauer spectra. With doping the stable-valence ion Fe^{3+} into the mixed-valence site of Jahn-Teller ions, such as $\text{Mn}^{2+}/\text{Mn}^{3+}$ or $\text{Mn}^{3+}/\text{Mn}^{4+}$, the long-range COO becomes the subject

of suppression by quenched disorder. The short range order is understood to preserve a favorite arrangements of Mn electronic configurations around the ^{57}Fe impurity dopants.

Via the quadrupole interactions and isomer shifts we explore the variety of structural and valence states adopted by the impurity. In addition, due to the layered structure the manifestations of vibrational anisotropy appears in Mössbauer line intensities, similarly to layered cuprates, which showed a notable Goldanskii-Karyagin effect (GKE)¹¹. In samples with preferred orientation, the texture effects are combined in Mössbauer spectra intensities with GKE and a technique is suggested to disentangle these effects. The same technique can be useful to determine the anisotropy in tensor material properties starting from the data obtained on the aligned powders. We illustrate the application of this technique to one of such properties, when the measurements is feasible again with the radiation of the same wavelength as in Mössbauer spectroscopy, however, realizable only on a large-scale synchrotron facility. This property is the anisotropic multicomponent phonon density of states (DOS), which request the single crystals for ordinary measurement¹², however, this work presents a proposal for determination of both DOS components using the aligned powders instead of a single crystal.

II. EXPERIMENTAL DETAILS

The layered A-site-ordered oxygen-saturated manganites $\text{LnBaMn}_{1.96}\text{Fe}_{0.04}\text{O}_6$ were prepared for $\text{Ln}=\text{Y, Gd, Sm, (Sm}_{0.9}\text{Nd}_{0.1}), (\text{Sm}_{0.1}\text{Nd}_{0.9}), \text{Nd, Pr and La}$. The oxides Ln_2O_3 and Fe_2O_3 were mixed with carbonates BaCO_3 and MnCO_3 . These mixtures were first annealed in 6N pure Ar (99.9999%) flow at 1350°C . This annealing has led to obtaining the oxygen-depleted phases $\text{LnBaMn}_{1.96}\text{Fe}_{0.04}\text{O}_5$. The synthesis of the oxygen-saturated "O₆" manganite is a two-step process as described previously¹⁰. The second step consisted of annealing in O_2 flow at low temperature (500°C). While in the first step of the oxygen-depletion the layered structure is formed of the alternating BaO and Y sheets interleaved by the MnO_2 'checkerboards', in the second step this structure is intercalated into Y-layer with the additional oxygen. A third family of manganites with the same cationic compositions was obtained in air (without layer-growing treatment in 6N Ar) and showed a simple perovskite-like disordered structure.

Rietveld profiles for both "O₅" and "O₆" families of layer-ordered manganites were obtained by means of a "Mac Science" diffractometer using Cu- K_α radiation ($\lambda=0.15405$ nm and 0.15443 nm). Mössbauer spectra were measured at room temperature. Isomer shifts are referred relatively $\alpha\text{-Fe}$. To prepare the oriented powder samples several methods were used. The powders were wet-spread in alcohol and dry-spread onto scotch tape or onto blotting-paper. The data were obtained for powders

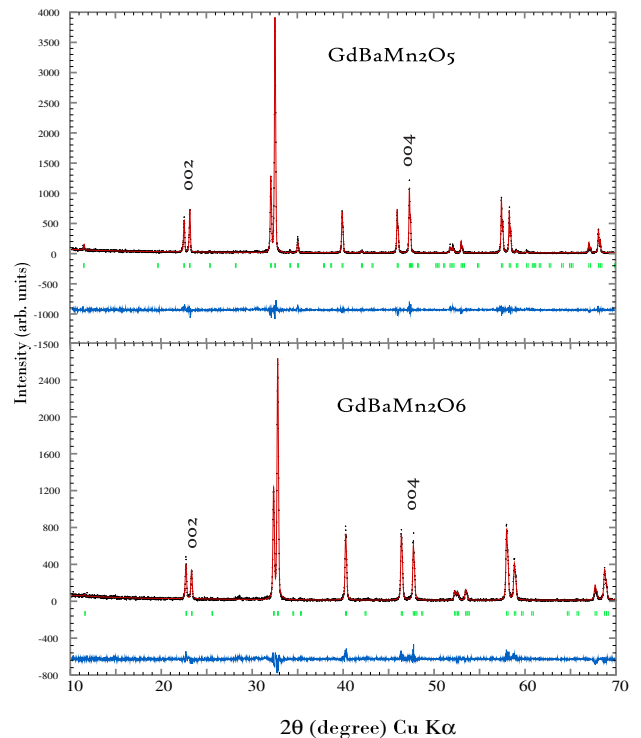


FIG. 2: Powder x-ray diffraction patterns of the tetragonal phases of $\text{GdBaMn}_{1.96}\text{Fe}_{0.04}\text{O}_5$ and $\text{GdBaMn}_{1.96}\text{Fe}_{0.04}\text{O}_6$ refined using space groups $P4/nmm$ (No. 129) and $P4/nmm$ (No.123), respectively.

oriented with their largest dimension in the plane-of the tape with a marked texture. Rietveld refinements for all diffraction profiles were carried out using FULLPROF program^{13,14}.

Measurements of magnetization were performed using a SQUID magnetometer in an applied field of 1 kOe at heating the samples from 5 K to T_{max} and then at cooling from $T = T_{\text{max}}$ down to 5 K. This measurement protocol was applied in $\text{LnBaMn}_{1.96}\text{Fe}_{0.04}\text{O}_6$ for $\text{Ln}=\text{Sm}$ with $T_{\text{max}}=400$ K and for $\text{Ln}=(\text{Nd}_{0.9}\text{Sm}_{0.1})$ with $T_{\text{max}}=370$ K. The magnetization in $\text{YBaMn}_{1.96}\text{Fe}_{0.04}\text{O}_6$ was measured first at heating from ambient temperature to $T_{\text{max}}=600$ K ($\text{Ln}=\text{Y}$) and then at cooling from $T = T_{\text{max}}$ down to 5 K. The sample was then remagnetized at 5K by setting the external field $H = 0 \pm 0.01$ kOe followed by reapplying $H = 1$ kOe. Finally, this sample magnetization was measured at heating up to 300 K.

III. RESULTS AND DISCUSSION

A. Structural considerations.

1. Room-temperature lattice parameters and symmetry groups

Prior to first reports on the manganites YBaMn_2O_5 ^{4,5,15} and $\text{LaBaMn}_2\text{O}_y$ ($y = 5$ and 6)^{6,16} which crystallized in the perovskite-like bilayered tetragonal structures, the ferrocuprate YBaCuFeO_5 with the same structure built up of bipyramidal layers was already known¹⁷ since 1988. On the other hand, the oxygen-rich ($y = 6$) layered manganite system had no prototype among cuprates. There exist two important features of the manganite systems, distinguishing them from the cuprate one. First, the layers of Ba and Ln develop in $\text{LaBaMn}_2\text{O}_y$ only if the system is deoxygenated ($y \sim 5$) at high-temperature synthesis. Excess of oxygen during the high-temperature annealing breaks the layered structure and create the disordered isotropic phase. Second, both the "O₅" and "O₆" structures exhibit the in-plane ordering mixed valence ions $\text{Mn}^{2+}/\text{Mn}^{3+}$ and $\text{Mn}^{3+}/\text{Mn}^{4+}$, respectively, both associated with COO. We observed that all of our x-ray profiles from "O₅" samples are perfectly fitted with the $P4/nmm$ model (Fig.1). The quality of fit was strongly declined when we attempted to fit the patterns in terms of $P4/mmm$ model. This result suggests that the COO is essentially preserved in our samples having the Fe ions placed into 2% of the Mn sites. However, from Mössbauer single-site spectra a COO meltdown is suggested, as shown below. Such a meltdown is not denotative of full randomness. Short range order in the arrangement of charges and orbitals is preserved. Indeed, since no superstructure reflections were observed, associated with lowering symmetry from $P4/mmm$ to $P4/nmm$, our Rietveld refinement preference for the symmetry group $P4/nmm$ indicates only that the COO is kept on a short range. In pure $\text{LaBaMn}_2\text{O}_5$, the supercell reflections are observable with electron diffraction⁶, while Fe-doping may broaden them and suppress their intensity to the level insufficient for observation. The coexistence of the preserved short-range COO with the doping-induced quenched disorder is discussed below along with Mössbauer spectra.

In contrast to the singular "O₅"-phase ($P4/nmm$ -phase), that is common for all the rare-earth elements, a few different modifications are known for the oxygen-saturated "O₆" A-site ordered layered manganites, depending on the size of Ln^{1,2,7,10}. All of them are built up of octahedral bilayers composed of octahedra distorted in one way or other. Our Rietveld refinements were carried out using several symmetry groups and structure models known from the literature^{1,2,7,10}. These treatments have shown that the tetragonal cell $a_p \times a_p \times 2a_p$ suits best (Fig.2) to all the samples in the layer-ordered oxygen-saturated family, with one

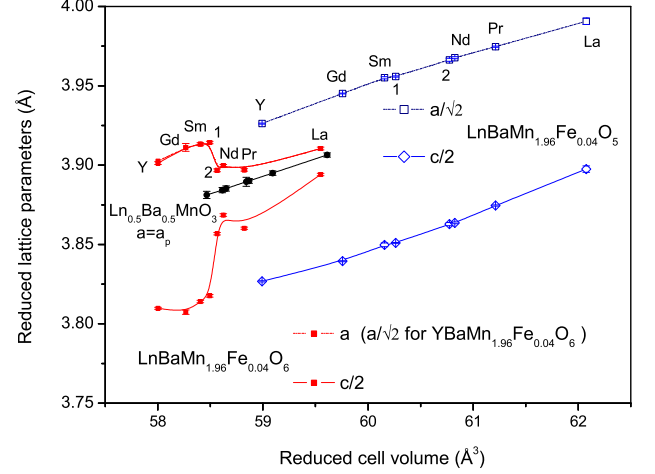


FIG. 3: Lattice parameters of the reduced perovskite-like cell vs. volume of this cell in 2% Fe-doped manganites. Mixed-rare-earths manganites $\text{Sm}_{0.9}\text{Nd}_{0.1}\text{BaMn}_{1.96}\text{Fe}_{0.04}\text{O}_y$ and $\text{Sm}_{0.1}\text{Nd}_{0.9}\text{BaMn}_{1.96}\text{Fe}_{0.04}\text{O}_y$ are denoted by "1" and "2", respectively.

exception of $\text{YBaMn}_{1.96}\text{Fe}_{0.04}\text{O}_6$. The structure of the latter was refined using the monoclinic symmetry (space group $P2_1$, No.3).

To summarize, the lattice cells were fitted with the volume double or quadruple of perovskite one ($V \cong 2a_p^3$ or $4a_p^3$) owing to the lattice parameters relations:

$$\begin{aligned} a = b &\cong \sqrt{2}a_p ; \quad c \cong 2a_p && \text{for } \text{LnBaMn}_{1.96}\text{Fe}_{0.04}\text{O}_5 \\ a = b &\cong a_p ; \quad c \cong 2a_p && \text{for } \text{LnBaMn}_{1.96}\text{Fe}_{0.04}\text{O}_6 \\ a &= a_p && \text{for } \text{Ln}_{0.5}\text{Ba}_{0.5}\text{Mn}_{0.98}\text{Fe}_{0.04}\text{O}_3 \end{aligned}$$

2. Distortions of perovskite cell

Comparing the parameters of reduced lattice cell (i.e. a distorted perovskite cell) one can analyze the extent of distortion depending on Ln, in function of the volume of the reduced cell. Fig. 3 summarizes the results of refinement of the lattice cell parameters. The reduced parameters $a/\sqrt{2}$ ($a/2$) and $c/2$ are plotted against the reduced cell volume $V/4$ ($V/2$). From Y to La the volume V varies in $\text{LnBaMn}_{1.96}\text{Fe}_{0.04}\text{O}_5$ within 5% and both a and c vary in the range of 1.7%. Distortion of the reduced cell can be calculated in $\text{LnBaMn}_2\text{O}_5$ as $D_5 = 2(a/\sqrt{2} - c/2)/(a/\sqrt{2} + c/2)$. From Y to La the distortion decreases from 2.56% to 2.36%, respectively. In the oxygen-saturated series, the distortion $D_6 = 2(a - c/2)/(a + c/2)$ does not show a stationary level from Y to La, but changes abruptly between Sm and Nd.

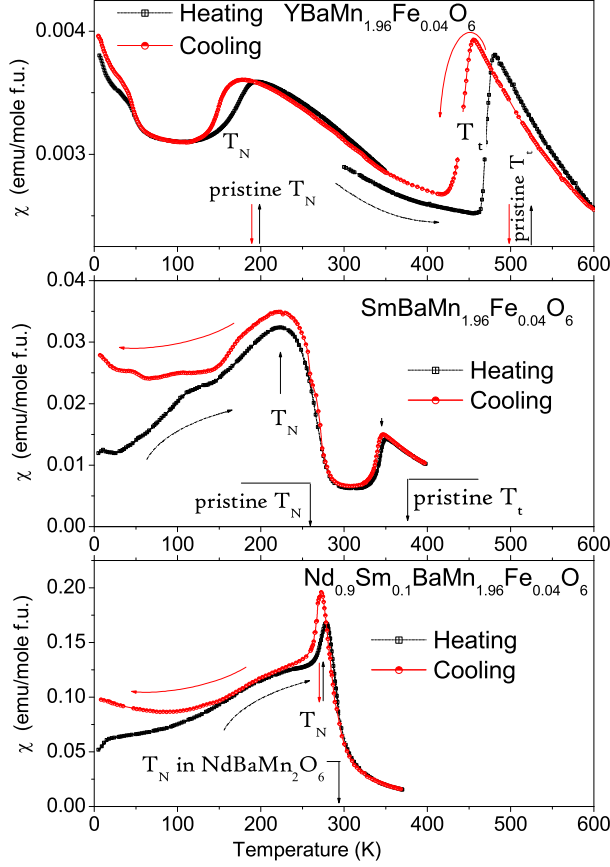


FIG. 4: Magnetic susceptibility M/H measured in the external field H of 1 kOe per mole of formula units in $\text{LnBaMn}_{1.96}\text{Fe}_{0.04}\text{O}_6$ for $\text{Ln}=\text{Y}$, Sm and $(\text{Nd}_{0.9}\text{Sm}_{0.1})$. The zero-field-cooled magnetization was measured at heating the samples up to T_{max} of 600 K ($\text{Ln}=\text{Y}$), 400 K ($\text{Ln}=\text{Sm}$) and 370 K ($\text{Ln}=\text{Nd}_{0.9}\text{Sm}_{0.1}$) and then at cooling from $T = T_{\text{max}}$. The arrows indicate the temperatures of phase transitions in corresponding pure $\text{LnBaMn}_2\text{O}_6$ without Fe substitution as reported previously^{1,8}.

3. Phase transitions

We observe in Fig. 4 that there occurs in $\text{LnBaMn}_{1.96}\text{Fe}_{0.04}\text{O}_6$ the phase transitions associated with COO and magnetic ordering. The same jumps and humps of susceptibility are observed as in the undoped $\text{LnBaMn}_2\text{O}_6$, however, the corresponding transition temperatures are suppressed. According to size of Ln three groups of the oxygen-saturated manganites were specified previously¹⁸ as $\text{Ln(I)}=(\text{Y}, \text{Tb}, \text{Dy}, \text{Ho})$, $\text{Ln(II)}=(\text{Sm}, \text{Eu}, \text{Gd})$ and $\text{Ln(III)}=(\text{Nd}, \text{Pr}, \text{La})$. A member from each of these families was investigated in this work for the effect of the Fe substituents on the transitions manifested in magnetic properties.

The transition sequences (temperatures T_t , T_N) in

the lightly (i.e. 2%) Fe-doped manganites are essentially same as in undoped manganites, but differ in details. In $\text{YBaMn}_{1.96}\text{Fe}_{0.04}\text{O}_6$ and $\text{SmBaMn}_{1.96}\text{Fe}_{0.04}\text{O}_6$, the highest in temperature jump of magnetization is associated with a structural transition, which is monoclinic-to-triclinic¹ or triclinic-to-monoclinic² for $\text{Ln}=\text{Y}$, and tetragonal-to-orthorhombic¹⁹ for $\text{Ln}=\text{Sm}$. Orbital ordering is now believed²⁰ to accompany these structural transition ($T = T_t$), while complete charge ordering is attributed^{1,10}, e.g. for $\text{Ln}=\text{Y}$, to a separate small hump shifted from T_t to lower temperature by $\Delta_t \approx 40$ K. In the undoped manganites, the temperature $T_{\text{CO}} = T_t - \Delta_t$ is associated with sharp localization of charge carriers. In the magnetization of $\text{YBaMn}_{1.96}\text{Fe}_{0.04}\text{O}_6$, the large jump is observed apparently without any small foregoing hump. Interestingly, similar disappearance of the hump in magnetization caused by Fe doping was reported for orbital ordering transition in BiMnO_3 ²¹. Smearing the transition over a broad temperature range induced by Fe substitution suppresses such a hump.

Another key feature of the doped systems stems from the fact that the values of T_t are slightly suppressed compared to undoped YBaMn_2O_6 and $\text{SmBaMn}_2\text{O}_6$ ^{1,8}. The suppression ranges are $\Delta T_t(2\%\text{Fe}) = 50\text{K}$ and 40K for $\text{Ln}=\text{Y}$ and Sm , respectively.

In contrast to similar values of ΔT_t , there occurs a large difference between the cases of $\text{Ln}=\text{Y}$ and Sm for the shift of the transition temperature with the reversal of temperature sweep direction. Such a shift is associated with an energy barrier for nucleation of a new phase within the region of overheating or undercooling the preceding phase. The hysteresis indicates strongly the first-order character of transition that was observed also in undoped YBaMn_2O_6 ¹. The large nucleation barrier is observed in YBaMn_2O_6 but not in $\text{SmBaMn}_2\text{O}_6$. This is in agreement with a very small structural distortion in $\text{SmBaMn}_2\text{O}_6$ at T_t as reported by Akahoshi et al¹⁹.

Temperatures of Neel (T_N) are also notably suppressed in both cases, as well as in the third group member, $\text{Nd}_{0.9}\text{Sm}_{0.1}\text{BaMn}_{1.96}\text{Fe}_{0.04}\text{O}_6$. The antiferromagnetic transitions humps were observed^{7,8} at 290 K and 250 K in undoped $\text{NdBaMn}_2\text{O}_6$ and $\text{SmBaMn}_2\text{O}_6$, respectively, therefore, the T_N value of 286 K is expected for the solid solution $\text{Nd}_{0.9}\text{Sm}_{0.1}\text{BaMn}_2\text{O}_6$. Remaining suppression $\Delta T_N \simeq 10\text{K}$ should be attributed to the effect of Fe substitution. Temperature ranges for sweep-reversal hysteresis around T_N are not much different between the three.

4. Preferred orientation

In both series of the layered manganites the samples displayed some degree of preferred orientation which is directly seen in x-ray diffraction patterns through an enhancement of the reflections of the type $00l$ (Fig.2). This indicates the platy habits of thin crystallites with the

easy cleavage planes parallel to the layers. Table 1 summarizes the results of refinement of the preferred orientation parameters.

Table 1. Parameters of March-Dollase function, G_1 and G_2 , Eq.(1), refined from x-ray diffraction patterns.

Ln	LnBaMn _{1.96} Fe _{0.04} O ₅			LnBaMn _{1.96} Fe _{0.04} O ₆		
	G_1	G_2	$\frac{M(0)}{M(\pi/2)}$	G_1	G_2	$\frac{M(0)}{M(\pi/2)}$
Y	0.61(3)	0.27(2)	5.64	N/A***	N/A***	—
Gd	0.61(1)	0.47(2)	3.88	0.57(3)	0.84(2)	1.88
Sm	0.73(1)	0.68(4)	1.71	0.76(3)	0.78(2)	1.38
1*	0.61(2)	0.74(3)	2.18	0.74(3)	0.76(2)	1.48
2**	0.80(2)	0.59(10)	1.57	0.97(5)	0.99(1)	1.00
Nd	0.47(4)	0.75(5)	3.80	0.55(10)	0.94(3)	1.35
Pr	0.45(6)	0.57(10)	7.56	0.46(22)	0.97(2)	1.31
La	0.68(2)	0.75(15)	1.74	0.96(3)	0.86(3)	1.03

*1: Sm_{0.9}Nd_{0.1}BaMn_{1.96}Fe_{0.04}O_x;

**2: Sm_{0.1}Nd_{0.9}BaMn_{1.96}Fe_{0.04}O_x

***Refinement with the uniaxial texture along $[00l]$ was not applicable by reason of monoclinic structure.

The March-Dollase (MD) function²² depends on three variables: the texture-axis-misfit angle θ and two profile-refinable parameters G_1 , G_2 (Ref.23),

$$M(\theta, G_1, G_2) = G_2 + \frac{1 - G_2}{[(G_1 \cos \theta)^2 + G_1^{-1} \sin \theta]^{\frac{3}{2}}} \quad (1)$$

That is to say, θ is the acute angle between the x-ray scattering vector $h\mathbf{a}^* + k\mathbf{b}^* + l\mathbf{c}^*$ and the axis of preferred orientation. In powders of single-crystalline particles, the preferred axis is dictated by the grain shape. The cylindrical-symmetry texture axis runs along the whisker-like or fiber-like crystals, but along the *normal* to the plate-like crystals. We fitted all our x-ray patterns with the uniaxial texture along the direction $[00l]$. The Eq.(1) describes the density of poles, which come into reflection position at a given Bragg angle $\theta = \theta_{hkl}$. From the viewpoint of conserving the scattering matter the function $M(\theta)$ is a true distribution function suitable for quantitative analysis. In this sense, the March-Dollase distribution is much better than Gaussian distribution, originally suggested by Rietveld²⁴. The parameter G_2 describes the fraction of the sample that is not textured and the parameter G_1 describes the degree of alignment within the textured fraction. The diffraction intensities are scaled by the distribution $M(\theta)$ which culminates at $\theta = 0$ for $G_1 < 1$, but at $\theta = \pi/2$ for $G_1 > 1$. Therefore, both plate-like and needle-like powders are refinable with the universal function $M(\theta)$. The domains $0 < G_1 < 1$ and $1 < G_1 < \infty$ correspond to the platy and acicular habits, respectively, while fully isotropic powder fits to $G_1 = 1$.

Two parameters of the textured sample anisotropy G_1 and G_2 presents the full set of texturing characteristics, however, it is convenient to simplify the sample comparison using the single parameter $M(0)/M(\pi/2)$ given by a combination of G_1 and G_2 . This ratio displays directly the enhancement of right-hand line within

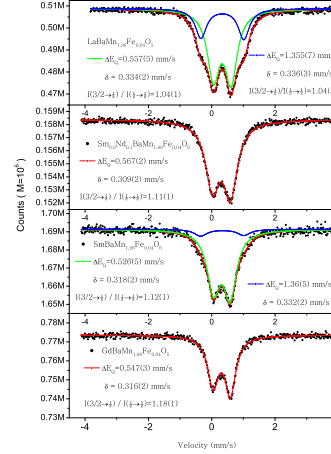


FIG. 5: Mossbauer spectra in oriented samples of ^{57}Fe -doped oxygen-poor series of the A-site ordered layered manganites $\text{LnBaMn}_{1.96}\text{Fe}_{0.04}\text{O}_5$. Fitted values of isomer shift, quadrupole splitting, and area asymmetry are indicated on the spectra. The spectra are fitted with one or two asymmetric doublets. Meltdown of $\text{Mn}^{2+}/\text{Mn}^{3+}$ charge order results in single-site spectra for ^{57}Fe , while residue of the second doublet is attributed to the remainder of the charge/orbital order.

the closely-spaced pairs $I(002)/I(100)$ and $I(004)/I(002)$ (Fig.2). From the Table 1 it becomes clear that $\text{LnBaMn}_{1.96}\text{Fe}_{0.04}\text{O}_5$ shows much stronger tendency to texturing than $\text{LnBaMn}_{1.96}\text{Fe}_{0.04}\text{O}_6$. This result could be explained by variations in crystallite size and aspect ratio.

Returning to the preparation conditions of these series of samples, one sees that $\text{LnBaMn}_{1.96}\text{Fe}_{0.04}\text{O}_6$ was prepared from $\text{LnBaMn}_{1.96}\text{Fe}_{0.04}\text{O}_5$ in oxygen at the temperature as low as 500°C . In such a low temperature process, the crystallites could be destroyed and diminished in size, but hardly could grow. It follows indeed from Fig.3 that the large compression of the lattice takes place at oxygenation. It was observed previously in $\text{GdBaMn}_2\text{O}_{5+x}$ ²⁵, that the rate of oxygen intercalation into the layered oxide is extremely high. Strains associated with the oxygenation are very large. The crystal cracking and breakup in lateral dimension are likely to accompany the oxygen intercalation. The crystal cracks and strains observed during oxygenation were attributed to orthorhombicity²⁵. We have stabilized the orthorhom-

bic phase $\text{GdBaMn}_2\text{O}_{5.5}$ using a more complicated sequence of thermal treatments²⁶. The orthorhombic distortion in $\text{GdBaMn}_2\text{O}_{5.5}$ is indeed much larger than either D_5 or D_6 , calculated above. Large distortion arises from channel-like structure of the half-filled layer $\text{LnO}_{0.5}$ and this could be the plausible origin of the crystal disintegrating with oxygenation²⁶.

B. Mössbauer spectroscopy

1. Oxygen-depleted phase $\text{LnBaMn}_{1.96}\text{Fe}_{0.04}\text{O}_5$

Mössbauer spectra in oriented samples of $\text{LnBaMn}_{1.96}\text{Fe}_{0.04}\text{O}_5$ are clearly asymmetric. In the samples with $\text{Ln}=\text{Gd}$ and $\text{Ln}=(\text{Sm}_{0.9}\text{Nd}_{0.1})$ the spectra are fitted with single asymmetric doublet. However, two doublets are crucial to fit the spectra for $\text{Ln}=\text{La}$ and Sm (Fig.5).

Spectral asymmetry increases from La towards Gd and this increase correlates with increasing distortion D_5 . The second doublet is not enough resolved to fit separately its asymmetry. Therefore, its asymmetry was fixed at fitting to be the same as the asymmetry of the major doublet.

As the size of Ln decreases we observe the systematic decrease in the area of second doublet. An exception from this series is made by the mixed rare-earth manganite $\text{Sm}_{0.9}\text{Nd}_{0.1}\text{BaMn}_{1.96}\text{Fe}_{0.04}\text{O}_5$ showing a single doublet, although the average size of $(\text{Sm}_{0.9}\text{Nd}_{0.1})$ is larger than the size of Sm, while $\text{SmBaMn}_{1.96}\text{Fe}_{0.04}\text{O}_5$ still shows a presence of the second doublet. However, this observation is in line with our interpretation of the single-site spectrum as originating from the meltdown of the charge order induced by the pointlike quenched disorder. Indeed, the additional pointlike disorder in $\text{Sm}_{0.9}\text{Nd}_{0.1}\text{BaMn}_{1.96}\text{Fe}_{0.04}\text{O}_5$ is related to disorder in the Ln site.

2. Coexistence of the short-range COO with quenched disorder

An important result appears in the fact that Fe sees the charge order broken more easily for smaller Ln by the same level of doping. The double-site spectrum in $\text{LaBaMn}_{1.96}\text{Fe}_{0.04}\text{O}_5$ evidences that the charge order is robust for $\text{Ln}=\text{La}$, so that the Fe species occupy both Mn(II) and Mn(III) sites, although the area ratio is 7:3 instead of 5:5 expected for random occupation. Such a random occupation might be expected only in case of long-range charge order. However, iron can adopt more easily its preferred site when the charge and orbital ordered domains decrease in size.

There occurs enough charge fluidity in $\text{GdBaMn}_{1.96}\text{Fe}_{0.04}\text{O}_5$ and in $\text{Sm}_{0.9}\text{Nd}_{0.1}\text{BaMn}_{1.96}\text{Fe}_{0.04}\text{O}_5$ to realize the unique surrounding for overwhelming majority of dopants.

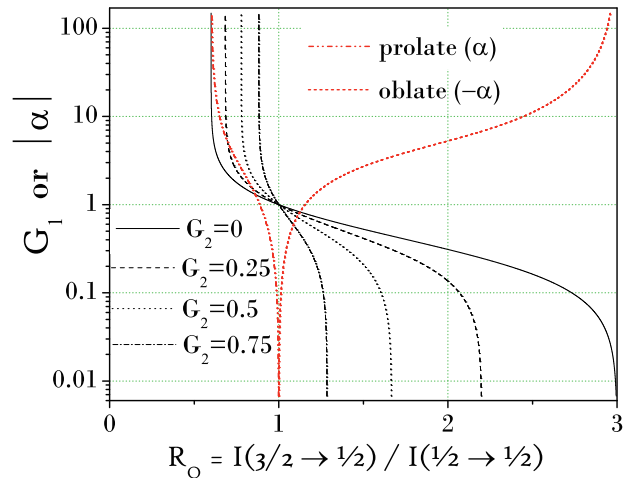


FIG. 6: Determination of the parameters of texture G_1 and vibrational anisotropy α starting from the ratio of line intensities of Mössbauer doublet. Either texture or GKE is supposed to be a single source of spectral asymmetry. Strength of preferred orientation G_1 is plotted vs. spectral asymmetry $R_Q = I_{\pm 1/2 \rightarrow \pm 3/2} / I_{\pm 1/2 \rightarrow \pm 1/2}$ for four values of the fraction of unoriented phase G_2 .

On the other hand, in $\text{LaBaMn}_{1.96}\text{Fe}_{0.04}\text{O}_5$ and in $\text{SmBaMn}_{1.96}\text{Fe}_{0.04}\text{O}_5$, we observe the robust COO that has a longer correlation lengths, such that a minor but significant part of dopants remains in a different surrounding.

The second doublet shows the same isomer shift but twice increased quadrupolar splitting. Both doublets originate from ^{57}Fe in pyramidal coordination, however, one of these doublets originates from the site having a larger apical distance and stronger Jahn-Teller character. Trying to understand the origin of difference between doping behaviors for large and small Ln's, let us compare the pyramidal interatomic distances in $\text{LaBaMn}_2\text{O}_5$ and in YBaMn_2O_5 as reported previously^{6,15}. The difference between Mn(II) and Mn(III) pyramids is similar for $\text{Ln}=\text{La}$ and Y, however, in YBaMn_2O_5 , both Mn(II) and Mn(III) pyramids are more elongated in apical dimension, and compressed in equatorial dimension. Such a distortion appears thus to facilitate the melting of the charge and orbital order around the doped Fe species.

3. Two sources of the doublet asymmetry

Known origins of the line area asymmetry in Mössbauer spectra are the preferred orientation of crystallites and vibrational anisotropy. In a random polycrystalline material, the ordinary single-site spectra in paramagnetic domain are the symmetric doublets. The equal intensities of both lines result from random-powder

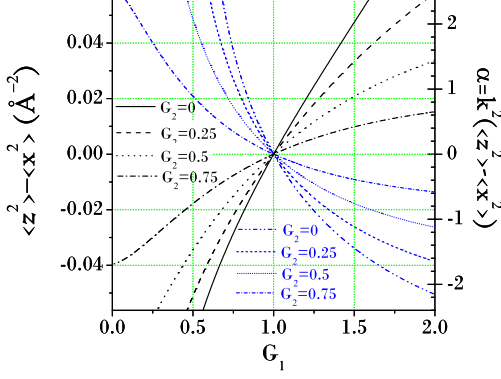


FIG. 7: The effective vibrational anisotropy parameters α and α/k^2 versus the equivalent degree of alignment G_1 at four values of the unoriented phase G_2 . The curves with positive slope refer to the true assignment, and the curves with negative slopes refer to the false assignment of the doublet lines to the $\pm 1/2 \rightarrow \pm 3/2$ and $\pm 1/2 \rightarrow \pm 1/2$ transitions.

averaging, unless GKE takes place. Preferred orientation would induce the asymmetry with or without GKE. We discuss first the separate occurrence of texture effects and GKE and start from the texture effects.

a. Texture effects Let us consider the doublet intensity ratio for a single crystallite. This ratio depends on the orientation of the wave vector of the incident x-ray quantum with respect to the axes of the electric field gradient (EFG) tensor of the site wherein the ^{57}Fe nucleus is located. The angular dependence of Clebsch-Gordan coefficients²⁷ results in the θ -dependent intensity ratio of the quadrupole doublet R_Q for each crystallite:

$$R_Q = \frac{I_{\pm 1/2 \rightarrow \pm 3/2}}{I_{\pm 1/2 \rightarrow \pm 1/2}} = \frac{1 + \cos^2 \theta}{2/3 + \sin^2 \theta} \quad (2)$$

When the unoriented powder is used for measuring the spectra the angular averaging gives $\langle \sin^2 \theta \rangle = 2/3$, $\langle \cos^2 \theta \rangle = 1/3$ and $R_Q = 1$. In case of oriented powder, using the MD texture function (Eq.1), we substitute $\langle \sin^2 \theta \rangle$ and $\langle \cos^2 \theta \rangle = 1 - \langle \sin^2 \theta \rangle$ with

$$\langle \sin^2 \theta \rangle \equiv V(G_1, G_2) = \int_0^1 M(\theta, G_1, G_2) \sin^3 \theta d\theta \quad (3)$$

where

$$V(G_1, G_2) = \frac{2}{3}G_2 + (1 - G_2)v(G_1) \quad (4)$$

$$v(G_1) = \frac{G_1^2}{\varepsilon^2(G_1)} - \frac{\beta(G_1)}{2\varepsilon^3(G_1)} \quad (5)$$

$$\varepsilon(G_1) = \sqrt{G_1^2 - G_1^{-1}} \quad (6)$$

$$\beta(G_1) = \ln(2G_1^3 + 2\sqrt{G_1^6 - G_1^3} - 1) \quad (7)$$

Both factors $\varepsilon(G_1)$ and $\beta(G_1)$ are imaginary for $0 < G_1 < 1$, however, $V(G_1)$ is real in full range $0 < G_1 < \infty$.

Rietveld analysis allows one to fit the parameters of the degree of alignment G_1 and the aligned fraction G_2 starting from a set of x-ray diffraction intensities. A similar problem can be formulated in Mossbauer spectroscopy: to determine G_1 and G_2 starting from the spectral asymmetry. In the area of small asymmetries, the effect of G_1 and G_2 on the asymmetry turns out to be nearly equal, as will be shown below. In Fig.6, the degree of alignment G_1 is plotted vs. the asymmetry R_Q for several values of the textured fraction G_2 .

b. Vibrational anisotropy The vibrational anisotropy α is also plotted in Fig.6 vs. R_Q . It is expressed through the absolute value of the wave vector for γ -radiation and the mean-square vibrational displacements along V_{zz} , and in perpendicular direction, $\alpha = k^2(\langle z^2 \rangle - \langle x^2 \rangle)$. This plot was calculated following the integral of each line intensity scaled with the angle-dependent Lamb-Mössbauer factor for uniaxial symmetry $\exp(-\alpha \cos^2 \theta)$:

$$R_Q(\alpha) = \frac{\int_0^{\pi/2} (1 + \cos^2 \theta) e^{-\alpha \cos^2 \theta} d\theta}{\int_0^{\pi/2} (2/3 + \sin^2 \theta) e^{-\alpha \cos^2 \theta} d\theta} \quad (8)$$


The Eq.(8) is appropriate in randomized powders of all our "O₆" phases, except $\text{YBaMn}_{1.96}\text{Fe}_{0.04}\text{O}_6$. The sigmoidal function $R_Q(\alpha)$ is decreasing from 3 to 0.6 when α is varied from $-\infty$ to $+\infty$. The inverse function $\alpha(R_Q)$ is shown in Fig.6 as a semilog plot, having two branches. The right-hand branch ($R_Q > 1$) corresponds to oblate, pancake-shaped ellipsoids of atomic thermal displacements (ATD), and the less-dispersive left-hand branch correspond to prolate, or cigar-like ATD.

From Fig.6 it becomes clear that the underbalanced line area ratio ($R_Q < 1$) is related to either prolate ATD or to acicular crystallite textures. The overbalanced ratio ($R_Q > 1$) is produced either by oblate ATD or by platy crystallite textures. Mixing these effects will be analysed below in §8.

4. Line assignment

The case $R_Q > 1$ refers in Eqs.(2,8) to stronger line $\pm 1/2 \rightarrow \pm 3/2$ and weaker line $\pm 1/2 \rightarrow \pm 1/2$. The line $\pm 1/2 \rightarrow \pm 3/2$ lies higher in energy than the line $\pm 1/2 \rightarrow \pm 1/2$ if $V_{zz} > 0$. *Vice versa*, if $V_{zz} < 0$, the lines swap the energy positions.

We attribute the more intense line in Fig. 5 to the transition $\pm 1/2 \rightarrow \pm 3/2$ assuming that the electric field gradient $V_{zz} > 0$ is oriented along z -axis perpendicular to layers. This is in agreement with the point charge model for pyramidal coordination²⁸. Thus, either oblate ATD or platy crystallite textures underlie the observed in Fig.5 spectral asymmetry. Among the reports of neutron

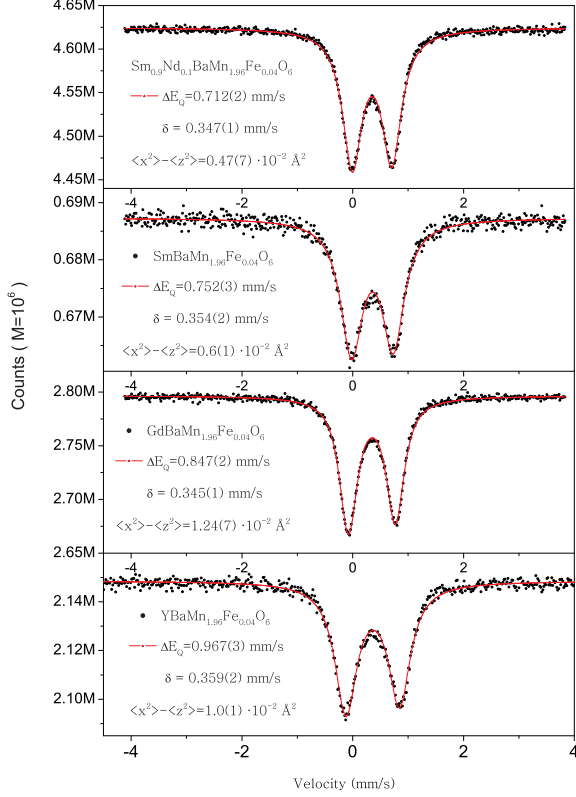

diffraction profile refinements in $\text{LnBaMn}_2\text{O}_5$, no data are known for an anisotropic ATD because all profiles were refined using B_{iso} ⁴⁻⁶. The anisotropic ATD, however, were refined previously for pyramidal coordination of YBaFeCuO_5 . The oblate ATD ellipsoids were never observed in pyramidal coordination. On the opposite, the ATD tensor shaped as very extended prolate 'cigar' was found in YBaFeCuO_5 ²⁹. Thus, the self-consistent combination is $V_{zz} > 0$ and prevailing asymmetry owing to platy-crystallite texture. The asymmetry would be reduced by prolate ATD, but not fully compensated.

The compensation effects can be described quantitatively if we find what texture parameters are equivalent to vibrational anisotropy parameter in its effect on asymmetry. Having arrived to the quantitative description of texture using the Eqs.(4-3) and Fig.6, we can now plot the vibrational parameter α vs. the equivalent degree of alignment G_1 (Fig.7). Due to the second parameter G_2

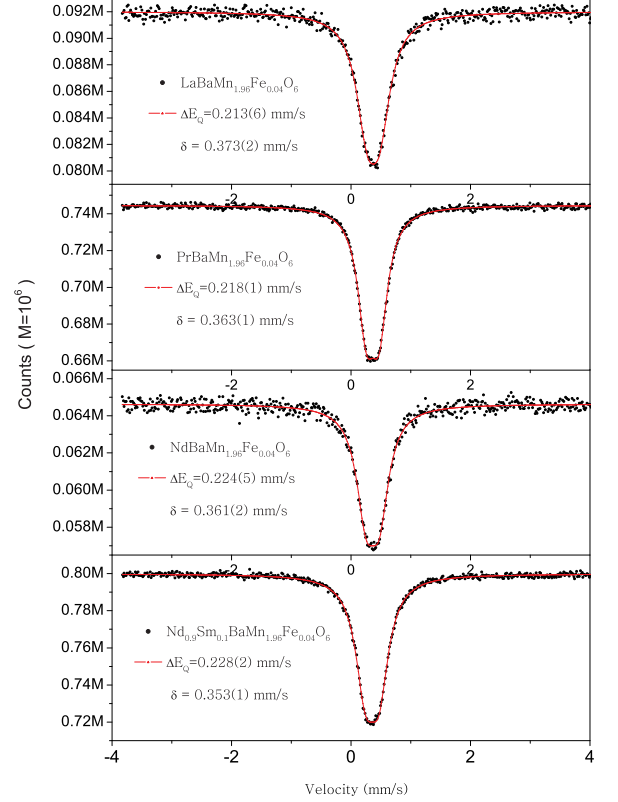


FIG. 9: Mossbauer spectra in the large-size-Ln subseries of the oxygen-rich series of the A-site ordered layered manganites $\text{LnBaMn}_{1.96}\text{Fe}_{0.04}\text{O}_6$ showing no COO transition. The spectra are fitted with one symmetric doublet.

a family of curves is produced, so that the effective α corresponding to a pair (G_1, G_2) can be found from the plot.

Knowledge of the EFG orientation and sign is not ubiquitous in Mössbauer spectroscopy. Since the correct attribution of the doublet lines to the $\pm 1/2 \rightarrow \pm 1/2$ and $\pm 1/2 \rightarrow \pm 3/2$ transitions is not always obvious, we plot in Fig.7 also the family of curves, which correspond to the false attribution. True attribution regions correspond to the bottom-left (oblate-platy) and top-right (prolate-acicular) quarters of the plot. False attribution regions correspond to the top-left (prolate-platy) and bottom-right (oblate-acicular) regions. In other words, the curves with positive slope refer to the true attribution, and the curves with negative slopes refer to the false attribution.

5. Oxygen-saturated phase $\text{LnBaMn}_{1.96}\text{Fe}_{0.04}\text{O}_6$

In contrast to $\text{LnBaMn}_{1.96}\text{Fe}_{0.04}\text{O}_5$ the left-hand line of the doublet turn to be more intense in the $\text{LnBaMn}_{1.96}\text{Fe}_{0.04}\text{O}_6$ series. The swap between the

$\pm 1/2 \rightarrow \pm 1/2$ and $\pm 1/2 \rightarrow \pm 3/2$ lines originates from the reversal of the sign of V_{zz} . Here again the negative sign of V_{zz} is consistent with the ionic point charge model, in which only the charges in first coordination sphere are taken into account²⁸. The case $R_Q > 1$ remains unchanged. The origin of asymmetry is therefore attributable to either platy habits of the crystallites, or to oblate vibrational ellipsoids. Both of them are expected *a priori* and their combined effect must be additive, but not partly extinguishing each other as in above case of $\text{LnBaMn}_{1.96}\text{Fe}_{0.04}\text{O}_5$. The anisotropies $\langle x^2 \rangle - \langle z^2 \rangle$ indicated on Fig.8 are the "effective" values given by the sum of true and equivalent to the pair (G_1, G_2) values.

The negative quadrupole splitting ΔE_Q decreases with decreasing the size of Ln. This is in agreement with the ionic point charge model²⁸. The absolute value of EFG correlates with distortion D_6 . In agreement with abrupt change of distortion between Sm and Nd as shown in Fig.3 the absolute value of ΔE_Q abruptly drops from 0.7 mm/s to 0.2 mm/s as the Ln size increases from Sm to Nd. The oxygen-saturated "O₆"-family can be thus divided into two subseries, according to their values of ΔE_Q . The spectra of small-size and large size Ln-subfamilies are shown in Figs. 8 and 9, respectively. This observation of two subfamilies agrees well with two types of behavior in the phase diagram reported previously^{1,9}. In the subfamily with small size Ln (Y, Gd, Sm) the COO is formed by the orbital stacked in sequence aabb along c-axis, and in the the large-size Ln-subfamily (Nd, Pr), the COO is not observed, while at lowering temperature the ferromagnetism first sets in at T_C , followed by the onset at $T_N < T_C$ of antiferromagnetic order of so-called A-type^{1,9}.

6. Cation-disordered phase $\text{Ln}_{0.5}\text{Ba}_{0.5}\text{Mn}_{0.98}\text{Fe}_{0.02}\text{O}_3$

Mössbauer spectra for the cation-disordered phase $\text{Ln}_{0.5}\text{Ba}_{0.5}\text{Mn}_{0.98}\text{Fe}_{0.02}\text{O}_3$ are shown in Fig.10. Iron is in octahedral coordination wherein the small quadrupole splitting can be associated either with the random short-range strain in oxygen sublattice or with the randomness in the (Ba,La)-coordination sphere of the ^{57}Fe nuclei.

7. Mössbauer line intensities versus March-Dollase parameters

The obtained formulas (4) and (3) allow to interpret the Mössbauer line intensities in terms of the Rietveld profile parameters G_1 and G_2 . In order to compare the Rietveld and Mössbauer results we present first in Fig.11 the contour plot of the doublet asymmetries R in function of G_1 and G_2 . Different values of R are shown by different colors. Total ranges of variation for the alignment degree is $0 < G_1 < \infty$ and for the fraction of unoriented phase $0 < G_2 < 1$. In Fig.11 the ranges $0 < G_1 < 2$ and $0 < G_2 < 1$ are presented.

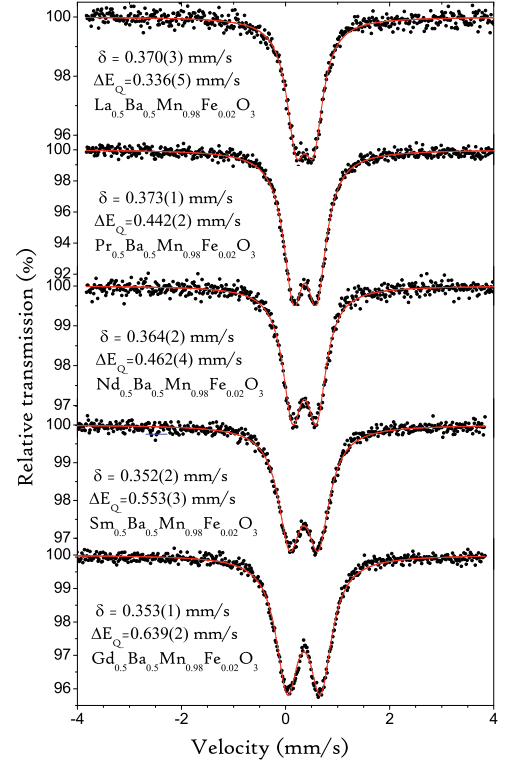


FIG. 10: Mössbauer spectra in disordered phase $\text{Ln}_{0.5}\text{Ba}_{0.5}\text{Mn}_{0.98}\text{Fe}_{0.02}\text{O}_3$. Fitted values of the quadrupole splittings and chemical shifts are indicated.

Since all the data in Table 1 indicate the platy habits with $0.25 < G_1 < 0.75$ in all our $\text{LnBaMn}_{1.96}\text{Fe}_{0.04}\text{O}_5$ samples, and with $0.5 < G_1 < 1$ we select these regions in Fig.12, (a) and (b), respectively. On the other hand, both these regions correspond to the small enough experimental asymmetries for the "O₅" and "O₆", respectively. The experimental Mössbauer doublet asymmetries from Figs. 5 and 8 are marked with the arc segments, and the data from Table 1 are indicated by chemical symbol of Ln at points with coordinates (G_1, G_2) . Interestingly, it turns out that the effects of G_1 and G_2 on the asymmetry turns out to be approximately equal.

The detailed analysis of Fig.12 confirms the suggested above picture. In the "O₅" series (Fig.12, top), the asymmetry indicated by symbols is stronger than the asymmetry indicated by arcs. It means that GKE reduces the total asymmetry indicated by arcs. In the "O₆" series (Fig.12, bottom), the asymmetry indicated by arcs is stronger than the asymmetry indicated by symbols. It means that GKE enhances the total asymmetry indicated by arcs.

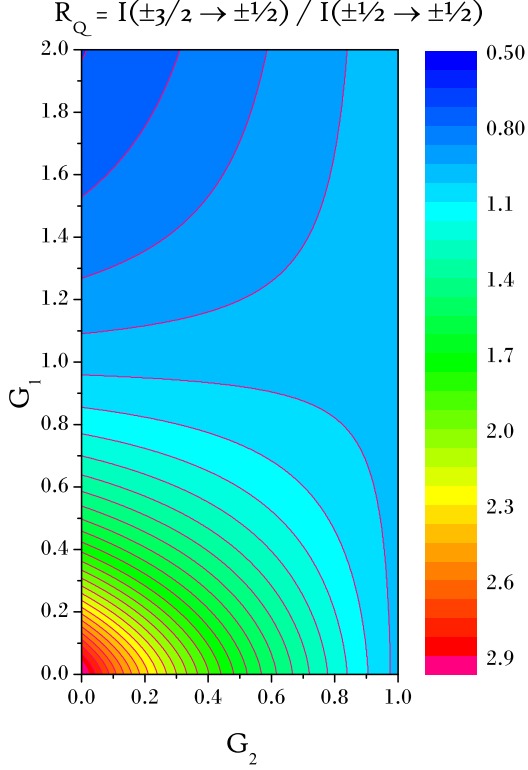


FIG. 11: Contour plot of the Mössbauer spectra asymmetry R versus G_1 and G_2 (Eqs. 4 and 3). The upper half of the plot corresponds to acicular habitus and the lower part of the plot correspond to the platy habitus of the crystals. Note that only the region of relatively weak degrees of alignment for acicular habitus is shown, while full range $0 < G_1 < 1$ is shown for platy habitus crystallites. The region of relatively weak alignments exhibits symmetric dependence of R on G_1 and G_2 .

8. Theory of GKE in oriented powders

The effects of texture and GKE on spectral asymmetry are only qualitatively considered above to be additive or extinguishing. To express it more exactly, the expression for intensity ratio was formulated³⁰,

$$R = \frac{\int_0^{\pi/2} M(\theta)(1 + \cos^2 \theta)e^{-\alpha \cos^2 \theta} d\theta}{\int_0^{\pi/2} M(\theta)(2/3 + \sin^2 \theta)e^{-\alpha \cos^2 \theta} d\theta} \quad (9)$$

however, the solutions were yet found either for texture effects, or for GKE, separately only. Substituting the MD function (Eq.1) for $M(\theta)$ we propose a general solution for the combined effect of texture and vibrational anisotropy. A replacement of $M(\theta, U, r)$ with the minimum texture function^{31,32} makes the Eq. (10) integrable:

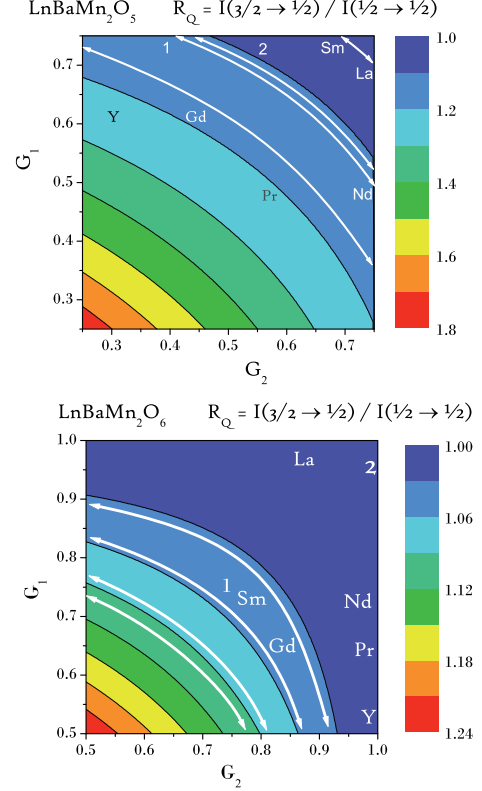


FIG. 12: Regions of R vs. G_1, G_2 plot corresponding to our samples of $\text{GdBaMn}_{1.96}\text{Fe}_{0.04}\text{O}_5$ (top panel) and $\text{GdBaMn}_{1.96}\text{Fe}_{0.04}\text{O}_6$ (bottom panel). The arcs show the spectral asymmetries from Figs. 5 and 8 and the element symbols indicate the texturing coordinates (G_1, G_2) of the samples from the Table 1.

$$R(\alpha) = \frac{(15V - 6)f(\alpha) + (12 - 15V)g(\alpha) + h(\alpha)}{(25V - 10)f(\alpha) + (28 - 45V)g(\alpha) - h(\alpha)} \quad (10)$$

Here $V = V(G_1, G_2)$, $f(\alpha) = {}_1F_1(\frac{1}{2}, \frac{3}{2}; -\alpha)$ is the Kummer confluent hypergeometric function, $g(\alpha) = (f(\alpha) - e^{-\alpha})/\alpha$ and $h(\alpha) = (30 - 45V)(3g(\alpha) - 2e^{-\alpha})/4\alpha$. The minimum texture function (MTF) compatible with the MD function was taken as follows:

$$\text{MTF}(x) = \left(\frac{15}{4} - \frac{45}{4}x^2\right)V(G_1, G_2) + \frac{15}{2}x^2 - \frac{3}{2} \quad (11)$$

with $x = \cos \theta$. The solution (10) gives the exact solution only for small asymmetries, because MTF is only a good approximation for the MD function for R close to 1. A perfect approximation for the broad range of asymmetries is given elsewhere³³.

C. Implications for the nuclear inelastic scattering (NIS) spectroscopy

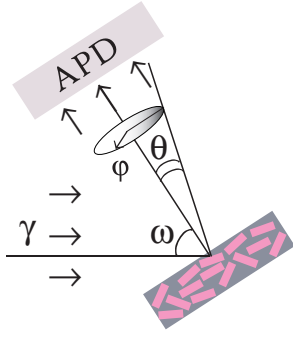


FIG. 13: Geometry of nuclear inelastic scattering experiment.

1. *Putting in use the Rietveld analysis for the NIS spectra on synchrotron radiation*

One of the problems, in which the well-oriented powders of platy or acicular crystallites can be useful is the problem of determination of the partial phonon density of states of ^{57}Fe in anisotropic materials using the NIS spectroscopy³⁴. The vibrational density of states is conventionally derived from measuring the NIS spectra in single crystals along different crystal axis. This Section presents a proposal for the novel NIS experiments using the oriented powder samples.

In the NIS spectrum of an anisotropic single crystal the phonon DOS is weighted by the squared projection of the phonon polarization vectors to the wave vector of the x-ray quantum¹². Three projected densities of states $g_\zeta(E)$ ($\zeta = x, y, z$) of an anisotropic layered material can be determined by measuring the single crystal spectra at three different orientations. In the uniaxially anisotropic material, the powder-averaged NIS spectrum is isotropic, however, measuring two spectra on a sample with preferred orientation of crystallites, $W(\omega_1)$ and $W(\omega_2)$ at different angles (Fig.13) provides the full basis for determination of both DOS functions $g_x(E)$ and $g_z(E)$. For this purpose the texture of a sample should be well enough characterized, using Rietveld analysis and Mössbauer spectroscopy.

The simplest experiment that we propose for measuring two components of the uniaxially anisotropic DOS on a oriented sample involves the sample stage rotated around the horizontal axis perpendicular to the incident beam (Fig.13). Therefore, it is worth to describe the DOS in terms of the angles θ , ω and the Rietveld MD function preferred orientation parameters G_1 and G_2 .

2. *Deriving the components of anisotropic vibrational DOS*

Let us launch the incident beam under the angle $\vartheta = \theta + \omega$ with respect to the preferred axis (z-axis) of a plate-like or a needle-like crystallite. Each DOS component is weighted by the projection of the phonon polarization vectors to the wave vector of the x-ray quantum, there-

fore, the phonon DOS projected on the direction defined by the angle ϑ can be written:

$$g_E(\vartheta) = g_z(E) \cos^2 \vartheta + g_x(E) \sin^2 \vartheta \quad (12)$$

Powder averaging of the DOS consists in integrating these two terms with the volume of crystallites $D(\vartheta, \phi) d\Omega$ whose z-axis lies within the cone shell element $d\Omega$ and result in

$$\langle g(E) \rangle = g_x(E) + \Delta g_{zx}(E) \int D(\vartheta, \phi) \cos^2 \vartheta d\Omega \quad (13)$$

Here the normalization of the texture function to unity and the notation $\Delta g_{zx}(E) = g_z(E) - g_x(E)$ are employed. The polar function $M(\theta, U, r)$, independent on the azimuth angle, is to replace $D(\vartheta, \phi)$ via the coordinate transform from the frame of the beam to the frame of the rotation stage. The ratio of angular elements $d\Omega_{\text{beam}}/d\Omega_{\text{stage}}$ is $\sin \vartheta d\vartheta d\phi / \sin \theta d\theta d\varphi$ and the Jacobian of this transform is $\sin \vartheta / \sin \theta$. Using

$$\cos \vartheta = \cos \theta \cos \omega - \sin \theta \sin \omega \cos \varphi \quad (14)$$

we obtain for the uniaxial symmetry

$$\langle \cos^2 \vartheta \rangle = \langle \cos^2 \theta \rangle \cos^2 \omega + \frac{1}{2} \langle \sin^2 \theta \rangle \sin^2 \omega \quad (15)$$

Using the integrated MD texture function (Eqs.4 and 3), we substitute $\langle \sin^2 \theta \rangle$ and $\langle \cos^2 \theta \rangle$ with $V(G_1, G_2)$ and $1 - V(G_1, G_2)$ and obtain

$$\langle \cos^2 \vartheta \rangle = [1 - V(G_1, G_2)] \cos^2 \omega + \frac{V(G_1, G_2)}{2} \sin^2 \omega \quad (16)$$

From the Eq.(13) a couple of measurements of DOS $g_1(E)$ and $g_2(E)$ at the angles ω_1 and ω_2 leads immediately to determination of both DOS components:

$$\Delta g_{zx}(E) = \frac{\Delta g_{12}(E)}{[1 - \frac{3}{2}V(G_1, G_2)] (\cos^2 \omega_1 - \cos^2 \omega_2)} \quad (17)$$

$$g_x(E) = g_{12}(E) - \frac{\Delta g_{12}(E)}{2} \frac{(\cos^2 \omega_1 + \cos^2 \omega_2)}{(\cos^2 \omega_1 - \cos^2 \omega_2)} \quad (18)$$

where $g_{12}(E) = g_1(E)/2 + g_2(E)/2$ and $\Delta g_{12}(E) = g_1(E) - g_2(E)$.

IV. CONCLUDING REMARKS

Two aspects of this study were dealt with the methodological and material issues. First, we proposed putting

the Rietveld analysis in use for nuclear inelastic scattering spectroscopy and developed the method of derivation of the anisotropic phonon DOS from the experiments on oriented powder samples.

Second, in the material aspect of investigating the structure of doped manganites we found a seemingly contradictory events of persistence of the charge-orbital order observed in magnetization and in lattice cell dimension, coexisting with the disordered-state single-site Mössbauer spectra in most of the samples, excluding $\text{LaBaMn}_{1.96}\text{Fe}_{0.04}\text{O}_5$, and, possibly, $\text{SmBaMn}_{1.96}\text{Fe}_{0.04}\text{O}_5$. However, a plausible interpretation of this combination of results is given suggesting the adaptiveness of the residual short-range COO towards the quenched disorder related to the random distribution of impurities.

In oxygen-saturated state ($y = 6$) the manganites exhibit the charge and orbital order at ambient temperature for $\text{Ln}=\text{Y, Gd, Sm}$, but unordered e_g -electronic system for $\text{Ln}=\text{La, Pr, Nd}$. Fourfold increase of quadrupole split-

ting was observed in charge and orbitally ordered manganites compared to unordered ones. This is in agreement with the jumplike increase of distortion of reduced perovskite-like cell in the charge and orbitally ordered structures. The light (i.e. with 2%) substitution of Mn by Fe suppresses the temperatures of structural and magnetic transitions by 20 to 50 K.

V. ACKNOWLEDGEMENTS

The authors acknowledge the financial support provided through joint JSPS-RFBR Grant 07-02-91201. The work at School of Engineering was additionally supported by Asahi Glass Foundation.

VI. REFERENCES

-
- * Corresponding author, rykov3@yahoo.com
- ¹ T. Nakajima, H. Kageyama, M. Ichihara, K. Ohoyama, H. Yoshizawa, and Y. Ueda, *J. Solid St. Chem.* **177**, 987 (2004).
 - ² A.J. Williams, J.P. Attfield, and S.A.T. Redfern, *Phys. Rev. B* **72**, 184426 (2005).
 - ³ A. I. Rykov, *Europhys. Lett.* **85** (2009) 16003.
 - ⁴ J.P. Chapman, J.P. Attfield, M. Molgg, C.M. Friend, and T.P. Beales, *Angew. Chem. Int. Ed. Engl.* **35**, 2482 (1996).
 - ⁵ J.A. McAlister, J.P. Attfield, *J. mater. Chem.* **8**, 1291 (1998).
 - ⁶ F. Millange, V. Caignaert, B. Domengès, and B. Raveau, *Chem. Mater.* **10**, 1974 (1998).
 - ⁷ T. Nakajima, H. Kageyama, H. Yoshizawa, K. Ohoyama, and Y. Ueda, *J. Phys. Soc. Jpn.* **72**, 3237 (2003).
 - ⁸ T. Nakajima, H. Yoshizawa and Y. Ueda, *J. Phys. Soc. Jpn.*, **73**, 2283 (2004).
 - ⁹ D. Akahoshi, Y. Okimoto, M. Kubota, R. Kumai, T. Arima, Y. Tomioka, and Y. Tokura, *Phys. Rev. B* **70**, 064418 (2004).
 - ¹⁰ T. Nakajima, H. Kageyama, Y. Ueda, *J. Phys. Chem. Solids*, **63**, 913 (2002).
 - ¹¹ A. Rykov, V. Caignaert, and B. Raveau, *J. Solid. St. Chem.* **109**, 295 (1994).
 - ¹² V.G. Kohn, A.I. Chumakov, R. Rüffer, *Phys. Rev. B* **58**, 8437 (1998).
 - ¹³ R.A. Young and D.B. Wiles, *Adv. X-ray. Anal.* **24**, 1, (1981).
 - ¹⁴ J. Rodriguez-Carvajal. *Physica B* **192**, 55 (1993).
 - ¹⁵ F. Millange, E. Suard, V. Caignaert, and B. Raveau, *Mat. Res. Bull.* **34**, 1 (1999).
 - ¹⁶ V. Caignaert, F. Millange, B. Domengès, and B. Raveau, *Chem. Mater.* **11**, 930 (1999).
 - ¹⁷ L. Er-Rakho, C. Michel, P. Lacorre and B. Raveau, *J. Solid State Chem.* **73** (1988) 531.
 - ¹⁸ T. Nakajima, H. Kageyama, H. Yoshizawa, and Y. Ueda, *J. Phys. Soc. Jpn* **71**, 2843 (2002)
 - ¹⁹ D. Akahoshi, M. Uchida, Y. Tomioka, T. Arima, Y. Matsui, and Y. Tokura, *Phys. Rev. Lett.* **90**, 177203 (2003).
 - ²⁰ Y. Ueda and T. Nakajima, *Progr. Solid St. Chem.* **35**, 397 (2007).
 - ²¹ A.A. Belik, N. Hayashi, M. Azuma, S. Muranaka., M. Takano, and E. Takayama-Muromachi, *J. Solid St. Chem.* **180**, 3401 (2007).
 - ²² Incorporated into FULLPROF program, <http://www-llb.cea.fr/fullweb/powder.htm>.
 - ²³ W.A. Dollase, *J. Appl. Cryst.* **19** (1986) 267-272.
 - ²⁴ H.M. Rietveld, *J. Appl. Cryst.* **2**, 65 (1969).
 - ²⁵ A.A. Taskin, A.N. Lavrov, Yoichi Ando, *Progr. Solid St. Chem.* **35** 481 (2007).
 - ²⁶ A.I. Rykov, Y. Ueda and K. Nomura, arXiv:0902.2027v1 [cond-mat.str-el].
 - ²⁷ G.K. Shenoy, G.M. Friedt, *Nucl. Inst. Meth.* **136**, 569 (1976).
 - ²⁸ A.I. Rykov, A. Ducouret, N. Nguyen, V. Caignaert, F. Studer and B. Raveau, *Hyperfine Interact.* **77** (1993) 277.
 - ²⁹ A.W. Mombrú, K. Prassides, C. Christides, R. Erwin, M. Pissas, C. Mitros, and D. Niarchos, *J. Phys.: Cond. Mat.* **10**, 1247 (1998).
 - ³⁰ H.-D. Pfannes and U. Gonser, *Appl. Phys.* **1**, 93 (1973).
 - ³¹ H.-D. Pfannes and H. Fisher, *Appl. Phys.* **13**, 317 (1977).
 - ³² J.-M. Greneche and F. Varret, *J. Phys.* **C15**, 5333 (1982).
 - ³³ A.I. Rykov, M. Seto, Y. Ueda and K. Nomura, arXiv:0902.1801v1 [cond-mat.mtrl-sci]
 - ³⁴ M. Seto, Y. Yoda, S. Kikuta, X.W. Zhang and M. Ando, *Phys. Rev. Lett.* **74**, 3828 (1995).

VII. FIGURE CAPTIONS

Fig.1. The crystal structures and symmetry groups of the layer-ordered $\text{LnBaMn}_2\text{O}_5$ (a), $\text{LnBaMn}_2\text{O}_6$ (b) and disordered $\text{Ln}_{0.5}\text{Ba}_{0.5}\text{MnO}_3$ (c).

Fig.2. Powder x-ray diffraction patterns of the

tetragonal phases of $\text{GdBaMn}_{1.96}\text{Fe}_{0.04}\text{O}_5$ and $\text{GdBaMn}_{1.96}\text{Fe}_{0.04}\text{O}_6$ refined using space groups $P4/nmm$ (No. 129) and $P4/mmm$ (No.123), respectively.

Fig.3. Lattice parameters of the reduced perovskite-like cell vs. volume of this cell. $\text{Sm}_{0.9}\text{Nd}_{0.1}\text{BaMn}_{1.96}\text{Fe}_{0.04}\text{O}_x$ and $\text{Sm}_{0.1}\text{Nd}_{0.9}\text{BaMn}_{1.96}\text{Fe}_{0.04}\text{O}_x$ are denoted by "1" and "2", respectively.

Fig.4. Magnetic susceptibility M/H measured in the external field H of 1 kOe per mole of formula units in $\text{LnBaMn}_{1.96}\text{Fe}_{0.04}\text{O}_6$ for $\text{Ln}=\text{Y}$, Sm and $(\text{Nd}_{0.9}\text{Sm}_{0.1})$. The zero-field-cooled magnetization was measured at heating the samples up to T_{max} of 600 K ($\text{Ln}=\text{Y}$), 400 K ($\text{Ln}=\text{Sm}$) and 370 K ($\text{Ln}=\text{Nd}_{0.9}\text{Sm}_{0.1}$) and then at cooling from $T = T_{\text{max}}$. The arrows indicate the temperatures of phase transitions in corresponding pure $\text{LnBaMn}_2\text{O}_6$ without Fe substitution as reported previously^{1,8}.

Fig.5. Mossbauer spectra in oriented samples of ^{57}Fe -doped oxygen-poor series of the A-site ordered layered manganites $\text{LnBaMn}_{1.96}\text{Fe}_{0.04}\text{O}_5$. Fitted values of isomer shift, quadrupole splitting, and area asymmetry are indicated on the spectra. The spectra are fitted with one or two asymmetric doublets. Meltdown of $\text{Mn}^{2+}/\text{Mn}^{3+}$ charge order results in single-site spectra for ^{57}Fe , while residue of the second doublet is attributed to the remainder of the charge/orbital order.

Fig.6. Determination of the parameters of texture G_1 and vibrational anisotropy α starting from the ratio of line intensities of Mössbauer doublet. Either texture or GKE is supposed to be a single source of spectral asymmetry. Strength of preferred orientation G_1 is plotted vs. spectral asymmetry $R_Q = I_{\pm 1/2 \rightarrow \pm 3/2} / I_{\pm 1/2 \rightarrow \pm 1/2}$ for four values of the fraction of unoriented phase G_2 .

Fig.7. The equivalent vibrational anisotropy parameter α versus degree of alignment G_1 at four values of the unoriented phase G_2 . The curves with positive slope refer to the true assignment, and the curves with negative

slopes refer to the false assignment of the doublet lines to the $\pm 1/2 \rightarrow \pm 3/2$ and $\pm 1/2 \rightarrow \pm 1/2$ transitions.

Fig.8. Mossbauer spectra in oriented samples of ^{57}Fe -doped oxygen-rich series of the charge and orbitally ordered layered manganites $\text{LnBaMn}_{1.96}\text{Fe}_{0.04}\text{O}_6$. The spectra are fitted with one asymmetric doublet. Meltdown of $\text{Mn}^{3+}/\text{Mn}^{4+}$ charge order results in single-site spectra for ^{57}Fe . Fitted values of isomer shift, quadrupole splitting, and area asymmetry are indicated on the spectra. The values of $\langle x^2 \rangle - \langle z^2 \rangle$ are the "effective" anisotropies given by the sum of true and equivalent to the pair (G_1, G_2) values.

Fig.9. Mossbauer spectra in the large-size-Ln subseries of the oxygen-rich series of the A-site ordered layered manganites $\text{LnBaMn}_{1.96}\text{Fe}_{0.04}\text{O}_6$ showing no COO transition. The spectra are fitted with one symmetric doublet.

Fig.10. Mössbauer spectra in disordered phase $\text{Ln}_{0.5}\text{Ba}_{0.5}\text{Mn}_{0.98}\text{Fe}_{0.02}\text{O}_3$. Fitted values of the quadrupole splittings and chemical shifts are indicated.

Fig.11. Contour plot of the Mössbauer spectra asymmetry R versus G_1 and G_2 (Eqs. 4 and 3). The upper half of the plot corresponds to acicular habitus and the lower part of the plot correspond to the platy habitus of the crystals. Note that only the region of relatively weak degrees of alignment for acicular habitus is shown, while full range $0 < G_1 < 1$ is shown for platy habitus crystallites. The region of relatively weak alignments exhibits symmetric dependence of R on G_1 and G_2 .

Fig.12. Regions of R vs. G_1, G_2 plot corresponding to our samples of $\text{GdBaMn}_{1.96}\text{Fe}_{0.04}\text{O}_5$ (top panel) and $\text{GdBaMn}_{1.96}\text{Fe}_{0.04}\text{O}_6$ (bottom panel). The arcs show the spectral asymmetries from Figs. 5 and 8 and the element symbols indicate the texturing coordinates (G_1, G_2) of the samples from the Table1.

Fig. 13. Geometry of nuclear inelastic scattering experiment.

* Corresponding author, rykov3@yahoo.com